

Competing effects of mass anisotropy and spin Zeeman coupling on the upper critical field of a mixed d - and s -wave superconductor

Wonkee Kim^{1,2}, Jian-Xin Zhu¹ and C. S. Ting^{1,2}

¹*Department of Physics and Texas Center for Superconductivity, University of Houston, Houston,
Texas 77204*

²*National Center for Theoretical Sciences, Hsinchu, Taiwan, Republic of China*

Abstract

Based on the linearized Eilenberger equations, the upper critical field (H_{c2}) of mixed d - and s -wave superconductors has been microscopically studied with an emphasis on the competing effects of mass anisotropy and spin Zeeman coupling. We find the mass anisotropy always enhance H_{c2} while the Zeeman interaction suppresses H_{c2} . As required by the thermodynamics, we find H_{c2} is saturated at zero temperature. We compare the theoretical calculations with recent experimental data of $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$.

PACS numbers: 74.20.-z, 74.20.Mn, 74.25.Bt

It has been a consensus¹ that a high- T_c cuprate superconductor has a d -wave pairing symmetry, and CuO_2 plane is responsible for superconductivity. However, a pure d -wave symmetry is appropriate only for a tetragonal lattice structure, an orthorhombic material such as $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (YBCO) is believed to have a subdominant s -wave component in the order parameter. The orthorhombicity in YBCO is originated from a mass anisotropy (MA) along a - and b -directions. In other words, m_a is larger than m_b . Such a discrepancy is mainly due to CuO chains in the b -direction.²

Based on the Ginzburg-Landau theory, Xu *et al.*³ have explored effects of the mass anisotropy to show that an s -wave component always coexists with a dominant d -wave component in the bulk order parameter. Belzig *et al.*⁴ have obtained the phase diagram of a mixed d - and s -wave superconductor in the quasiclassical theory,⁵ and shown that the mass anisotropy gives rise to a non-zero s -wave component.

In this paper, we shall investigate effects of the MA on the upper critical field (H_{c2}) of a mixed d - and s -wave superconductor, based on the quasiclassical theory, using a quantum mechanical method we have developed in Ref.⁶ and compare a theoretical result with recent experimental data.⁷ We also take into account the paramagnetic Zeeman interaction (ZI) because H_{c2} of a high- T_c superconductor is large at low temperature. As in Ref.^{3,4}, we neglect any other effects associated with the chains. For example, we assume that lattice constants along a - and b -directions have the same value.

Since the calculation of H_{c2} is a quantum mechanical problem of a charged particle in a constant magnetic field,⁶ first of all we need to check if solvable is a problem of a charged particle with two different effective masses along x - and y -directions, m_x and m_y , respectively, in a constant magnetic field $\mathbf{H} = \nabla \times \mathbf{A} = H\hat{\mathbf{z}}$. In the symmetric gauge, the Hamiltonian $\mathcal{H}$ of the particle is given by

$$\begin{aligned}\mathcal{H} &= \frac{1}{2m_x}(p_x + \frac{e}{2}Hy)^2 + \frac{1}{2m_y}(p_y - \frac{e}{2}Hx)^2 \\ &= \frac{1}{2m_x}(p_x^2 + \lambda p_y^2) + \frac{eH}{2m_x}(yp_x - \lambda xp_y) + \frac{e^2 H^2}{8m_x}(y^2 + \lambda x^2),\end{aligned}\tag{1}$$

where $\lambda = m_x/m_y$. Introducing operators a_x and a_y such that

$$a_x = \frac{1}{\sqrt{2m_x\omega_0}}(m_x\omega_0\sqrt{\lambda}x + ip_x), \quad (2)$$

and

$$a_y = \frac{1}{\sqrt{2m_x\omega_0}}(m_x\omega_0 y + i\sqrt{\lambda}p_y), \quad (3)$$

where $\omega_0 = |e|H/2m_x$, $\mathcal{H}$ becomes

$$\mathcal{H} = \omega_0[a_x^+a_x + a_y^+a_y + \sqrt{\lambda} + i(a_x^+a_y - a_y^+a_x)]. \quad (4)$$

Let us introduce a new operator $b = (a_x + ia_y)/\sqrt{2\sqrt{\lambda}}$ to simplify $\mathcal{H}$; then, we obtain

$$\mathcal{H} = \omega_c \left(b^+b + \frac{1}{2} \right), \quad (5)$$

with $[b, b^+] = 1$, $[b, \mathcal{H}] = \omega_c b$, and $[b^+, \mathcal{H}] = -\omega_c b^+$, where $\omega_c = |e|H/\sqrt{m_x m_y}$. It shows that the problem we are considering reduces to that of a simple harmonic oscillator, and consequently H_{c2} for an anisotropic mixed d - and s -wave superconductor can be exactly calculated.

In the calculation of H_{c2} , we choose $[110]$ and $[-110]$ as x and y axis, respectively. An electron spectrum $\epsilon(\mathbf{k})$ then changes from $k_a^2/2m_a + k_b^2/2m_b$ to $k^2/2m + ck_x k_y/m$. Here we have defined $m_a = m/(1-c)$ and $m_b = m/(1+c)$, where a small quantity c is introduced to represent the degree of mass anisotropy. The Fermi surface (FS) now is elliptical, and the density of state $N(\phi)$ on FS becomes $N_0(0)/[1 + c \sin(2\phi)]$. By considering the anisotropy effect as a perturbation, we may assume that the order parameter can be still expanded in terms of the set of unperturbed eigenstates $\{f_N(\mathbf{R})\}$. In Ref.⁶, we have shown that the (singlet) order parameter is written as $A_0^{(d)}|0\rangle_d + A_2^{(s)}|2\rangle_s + A_4^{(d)}|4\rangle_d$ near H_{c2} , where we denote $|N\rangle_{d(s)}$ as eigenstates f_N of $d(s)$ channel. However, we expect that some other states such as $|0\rangle_s$, $|1\rangle_{s(d)}$, and $|2\rangle_d$ may involve in the order parameter due to the perturbation. The linear combination of these states for the order parameter near H_{c2} will be determined by the symmetry of the system.

The linearized Eilenberger equation is written as:⁸

$$\hat{L}f(\omega, \mathbf{k}, \mathbf{R}) + i\text{sgn}(\omega)\mu_0^*\mathbf{H} \cdot [\boldsymbol{\sigma}f(\omega, \mathbf{k}, \mathbf{R}) - f(\omega, \mathbf{k}, \mathbf{R})\boldsymbol{\sigma}^{tr}] = 2\pi\Delta(\mathbf{R}, \mathbf{k}) , \quad (6)$$

with

$$\Delta(\mathbf{R}, \mathbf{k}) = T \sum_{\omega} \langle V(\mathbf{k}, \mathbf{k}') f(\omega, \mathbf{k}', \mathbf{R}) \rangle_{FS} , \quad (7)$$

and

$$\hat{L} = 2|\omega| + i\text{sgn}(\omega)\mathbf{v}_F \cdot \boldsymbol{\Pi}. \quad (8)$$

Here $f(\omega, \mathbf{k}, \mathbf{R})$ is a quasiclassical Green's function, $\boldsymbol{\sigma} = (\sigma_x, \sigma_y, \sigma_z)$ are Pauli matrices, ω is the Matsubara frequency, μ_0^* can be interpreted as an effective magnetic moment of a quasi-electron with a mass anisotropy ($m_a \neq m_b$), which will be considered as a phenomenological parameter associated with a coupling strength between an electron spin and a magnetic field. The symbol $\langle \cdots \rangle_{SF} = \int \frac{d\phi'}{2\pi} N(\phi') \cdots$ represents the angular average over the Fermi surface. Since $\mathbf{v}_F = v_{Fa}\hat{\mathbf{a}} + v_{Fb}\hat{\mathbf{b}}$ and $\boldsymbol{\Pi} = -i\nabla_{\mathbf{R}} - 2e\mathbf{A} = \Pi_a\hat{\mathbf{a}} + \Pi_b\hat{\mathbf{b}}$ with $\hat{\mathbf{a}}$ and $\hat{\mathbf{b}}$ being unit vectors along the a and b directions,

$$\mathbf{v}_F \cdot \boldsymbol{\Pi} = (v_{Fx} + cv_{Fy})\Pi_x + (v_{Fy} + cv_{Fx})\Pi_y , \quad (9)$$

with $v_{Fx,y} = k_{Fx,y}/m$ in the x - y coordinate system. The pairing interaction in this coordinate system can be written as

$$V(\phi, \phi') = V_s + V_d \sin(2\phi) \sin(2\phi'), \quad (10)$$

where $\phi = \tan^{-1}(k_y/k_x)$.

For the singlet pairing, $f = f_0 i\sigma_y$ and $\Delta = \Delta_0 i\sigma_y$. Using the inverse of the operator $\hat{L}_{op} = \hat{L} + i\text{sgn}(\omega)\mu_0^*H$, which admits the representation

$$\hat{L}_{op}^{-1} = \int_0^\infty ds \exp(-s\hat{L}_{op}) , \quad (11)$$

we show

$$f_0 = 2\pi \int_0^\infty ds e^{-s[\hat{L} + 2i\text{sgn}(\omega)\mu_0^*H]} \Delta_0 . \quad (12)$$

Substituting Eq. (12) into Eq. (7), we obtain the linearized gap equation of an anisotropic mixed d - and s -wave superconductor as follows:

$$\begin{aligned} \Delta_0(\mathbf{R}, \phi) = 2\pi T \sum_{\omega} \langle V(\phi, \phi') \int d\xi e^{-\xi[2|\omega| + i\text{sgn}\omega \mathbf{v}_F \cdot \mathbf{\Pi}]} \\ \times \cos(2\mu_0^* H \xi) \Delta_0(\mathbf{R}, \phi') \rangle_{SF}. \end{aligned} \quad (13)$$

It is easy to see that $\Delta_0(\mathbf{R}, \phi)$ turns out to be $\Delta_s(\mathbf{R}) + \Delta_d(\mathbf{R}) \sin(2\phi)$ because of the pairing interaction $V(\phi, \phi')$ in Eq. (10).

Let us, first of all, consider equations to determine T_c of such a superconductor. Setting $H = 0$, we obtain

$$\Delta_s = N_0 V_s \left(1 + \frac{c^2}{2}\right) \ln \frac{2e^{\gamma} \omega_D}{\pi T_c} \Delta_s - N_0 V_s \left(\frac{c}{2}\right) \ln \frac{2e^{\gamma} \omega_D}{\pi T_c} \Delta_d, \quad (14)$$

and

$$\Delta_d = -N_0 V_d \left(\frac{c}{2}\right) \ln \frac{2e^{\gamma} \omega_D}{\pi T_c} \Delta_s + N_0 V_d \left(\frac{1}{2} + \frac{3}{8} c^2\right) \ln \frac{2e^{\gamma} \omega_D}{\pi T_c} \Delta_d. \quad (15)$$

In order to calculate T_c of an anisotropic mixed d - and s -wave superconductor, it is convenient to introduce the transition temperature $T_{d(s)}$ of the anisotropic $d(s)$ -wave superconductor such that $N_0 V_s \left(1 + \frac{c^2}{2}\right) \ln \frac{2e^{\gamma} \omega_D}{\pi T_s} = 1$, and $N_0 V_d \left(\frac{1}{2} + \frac{3}{8} c^2\right) \ln \frac{2e^{\gamma} \omega_D}{\pi T_d} = 1$. Then, T_c can be expressed in terms of $T_{d(s)}$ as follows:

$$\left(1 + \frac{c^2}{2}\right) \left(\frac{1}{2} + \frac{3}{8} c^2\right) \ln \frac{T_s}{T_c} \ln \frac{T_d}{T_c} = \left(\frac{\tilde{c}}{2}\right)^2, \quad (16)$$

where $\tilde{c} = c \sum_{n=0}^{n_D} (n+1/2)^{-1}$ with $\omega_D = (2n_D + 1)\pi T_c$. Here we would like to point out that a phenomenological value $T_c \simeq \frac{1}{2}(T_d + T_s) + \frac{1}{2}\sqrt{(T_d - T_s)^2 + 8\tilde{c}^2 T_d T_s}$ can be achieved only if $T_s \simeq T_d \simeq T_c$. If $T_s \ll T_d$, T_c has to be numerically calculated.

Following Ref.⁶, we expand $\Delta_{d(s)}(\mathbf{R})$ in terms of $\{f_N(\mathbf{R})\}$, namely, $\Delta_{d,s}(\mathbf{R}) = \sum_N A_N^{(d,s)} f_N(\mathbf{R})$, to obtain

$$\begin{aligned} \Delta_s(\mathbf{R}) = V_s \sum_N A_N^{(s)} \int d\xi \sum_m \sum_{n=0}^N \Phi_{n,m}(\xi, N) C_{n,m}^{(s)}(\xi, c) f_{N-n+m}(\mathbf{R}) \\ + V_s \sum_N A_N^{(d)} \int d\xi \sum_m \sum_{n=0}^N \Phi_{n,m}(\xi, N) C_{n,m}^{(sd)}(\xi, c) f_{N-n+m}(\mathbf{R}), \end{aligned} \quad (17)$$

and

$$\begin{aligned}\Delta_d(\mathbf{R}) = & V_d \sum_N A_N^{(s)} \int d\xi \sum_m \sum_{n=0}^N \Phi_{n,m}(\xi, N) C_{n,m}^{(sd)}(\xi, c) f_{N-n+m}(\mathbf{R}) \\ & + V_d \sum_N A_N^{(d)} \int d\xi \sum_m \sum_{n=0}^N \Phi_{n,m}(\xi, N) C_{n,m}^{(d)}(\xi, c) f_{N-n+m}(\mathbf{R}),\end{aligned}\quad (18)$$

where

$$\begin{aligned}\Phi_{n,m}(\xi, N) = & 2\pi T N_0 \sum_{\omega} e^{-2|\omega|\xi} e^{-|e|H\left(\frac{v_F\xi}{\sqrt{2}}\right)^2} \cos(2\mu_0^* H \xi) \\ & \times \frac{1}{\sqrt{m!n!}} \binom{N}{n}^{1/2} \binom{N-n+m}{m}^{1/2} [-|e|H(v_F\xi)^2]^{(n+m)/2}\end{aligned}$$

if $(n+m)$ is even and $\Phi_{n,m}(\xi, N) = 0$ if $(n+m)$ is odd, and

$$\begin{aligned}C_{n,m}^{(j)}(\xi, c) = & \int \frac{d\phi}{2\pi} \frac{\sin(2\phi)^j}{[1 + c \sin(2\phi)]} \exp \left\{ -|e|H \left(\frac{v_F\xi}{\sqrt{2}} \right)^2 [2c \sin(2\phi) + c^2] \right\} \\ & \times (e^{-i\phi} - ice^{i\phi})^m (e^{i\phi} + ice^{-i\phi})^n\end{aligned}$$

with $C_{n,m}^{(0)} \equiv C_{n,m}^{(s)}$, $C_{n,m}^{(1)} \equiv C_{n,m}^{(sd)}$ and $C_{n,m}^{(2)} \equiv C_{n,m}^{(d)}$. (See Appendix A for the detailed derivation.) It is necessary to investigate the symmetry properties of $C_{n,m}^{(j)}$ to calculate H_{c2} as we have mentioned early. Since c is a small quantity, we may expand the integrand of $C_{n,m}^{(j)}$ up to the c^2 order. After a careful investigation of $C_{n,m}^{(j)}$, we find

$$C_{n,m}^{(0)} \propto \frac{\sin[(m-n)\pi]}{(n-m+4)(n-m+2)(n-m)(n-m-2)(n-m-4)}, \quad (19)$$

$$C_{n,m}^{(1)} \propto \frac{C_{n,m}^{(0)}}{(n-m+6)(n-m-6)}, \quad (20)$$

and

$$C_{n,m}^{(2)} \propto \frac{C_{n,m}^{(1)}}{(n-m+8)(n-m-8)}. \quad (21)$$

As one can easily see, $C_{n,m}^{(0)} \neq 0$ only if $|n-m| = 0, 2, 4$, $C_{n,m}^{(1)} \neq 0$ only if $|n-m| = 0, 2, 4, 6$, and $C_{n,m}^{(2)} \neq 0$ only if $|n-m| = 0, 2, 4, 6, 8$. We also find other symmetry properties of $C_{n,m}^{(j)}$ such as $C_{n,m}^{(j)} = -C_{m,n}^{(j)}$ if $|n-m| = 2, 6$, and $C_{n,m}^{(j)} = C_{m,n}^{(j)}$ if $|n-m| = 4, 8$. These properties

are still valid even if we expand $C_{n,m}^{(j)}$ up to the c^4 order. We, thus, know that $|2N\rangle_{d(s)}$ do not couple to $|2N+1\rangle_{d(s)}$ but to $|2N\rangle_{d(s)}$, and vice versa. Consequently, we expect that the order parameter is represented by $\sum_N [A_{2N}^{(d)} |2N\rangle_d \sin(2\phi) + A_{2N}^{(s)} |2N\rangle_s]$ near H_{c2} ; in other words, H_{c2} is determined by such coefficients as $A_{2N}^{(d)}$ and $A_{2N}^{(s)}$.

Using the orthonormality of $\{f_N\}$, we obtain the equation for the coefficients $A_N^{(s)}$ and $A_N^{(d)}$ from which H_{c2} will be calculated as follows:

$$\begin{aligned} A_m^{(s)} = & V_s \sum_N A_N^{(s)} \int d\xi \sum_{n=0}^N \Phi_{n,m+n-N}(\xi, N) C_{n,m+n-N}^{(0)} \\ & + V_s \sum_N A_N^{(d)} \int d\xi \sum_{n=0}^N \Phi_{n,m+n-N}(\xi, N) C_{n,m+n-N}^{(1)}, \end{aligned} \quad (22)$$

and

$$\begin{aligned} A_m^{(d)} = & V_d \sum_N A_N^{(s)} \int d\xi \sum_{n=0}^N \Phi_{n,m+n-N}(\xi, N) C_{n,m+n-N}^{(1)} \\ & + V_d \sum_N A_N^{(d)} \int d\xi \sum_{n=0}^N \Phi_{n,m+n-N}(\xi, N) C_{n,m+n-N}^{(2)} \end{aligned} \quad (23)$$

with $m+n-N \geq 0$, and $|m-N| = 0, 2, 4$ for $C_{n,m+n-N}^{(0)}$, $|m-N| = 0, 2, 4, 6$ for $C_{n,m+n-N}^{(1)}$, and $|m-N| = 0, 2, 4, 6, 8$ for $C_{n,m+n-N}^{(2)}$. The equations to determine H_{c2} are given by $m = 0, 2, 4, \dots$, namely,

$$\begin{aligned} A_0^{(s)} = & V_s \int d\xi \left[A_0^{(s)} \Phi_{0,0}^0 C_{0,0}^{(s)} + A_2^{(s)} \Phi_{2,0}^2 C_{2,0}^{(s)} + A_4^{(s)} \Phi_{4,0}^4 C_{4,0}^{(s)} \right. \\ & \left. + A_0^{(d)} \Phi_{0,0}^0 C_{0,0}^{(sd)} + A_2^{(d)} \Phi_{2,0}^2 C_{2,0}^{(sd)} + A_4^{(d)} \Phi_{4,0}^4 C_{4,0}^{(sd)} \dots \right] \\ A_2^{(s)} = & V_s \int d\xi \left[A_0^{(s)} \Phi_{0,2}^0 C_{0,2}^{(s)} + A_2^{(s)} \sum_{i=0}^2 \Phi_{i,i}^2 C_{i,i}^{(s)} + A_4^{(s)} \sum_{i=0}^2 \Phi_{2+i,i}^4 C_{2+i,i}^{(s)} \dots \right. \\ & \left. + A_0^{(d)} \Phi_{0,2}^0 C_{0,2}^{(sd)} + A_2^{(d)} \sum_{i=0}^2 \Phi_{i,i}^2 C_{i,i}^{(sd)} + A_4^{(d)} \sum_{i=0}^2 \Phi_{2+i,i}^4 C_{2+i,i}^{(sd)} \dots \right] \\ A_4^{(s)} = & V_s \int d\xi \left[A_0^{(s)} \Phi_{0,4}^0 C_{0,4}^{(s)} + A_2^{(s)} \sum_{i=0}^2 \Phi_{i,2+i}^2 C_{i,2+i}^{(s)} + A_4^{(s)} \sum_{i=0}^4 \Phi_{i,i}^4 C_{i,i}^{(s)} \dots \right. \\ & \left. + A_0^{(d)} \Phi_{0,4}^0 C_{0,4}^{(sd)} + A_2^{(d)} \sum_{i=0}^2 \Phi_{i,2+i}^2 C_{i,2+i}^{(sd)} + A_4^{(d)} \sum_{i=0}^4 \Phi_{i,i}^4 C_{i,i}^{(sd)} \dots \right], \\ & \vdots \end{aligned}$$

and similar equations of $A_0^{(d)}, A_2^{(d)}, A_4^{(d)}, \dots$. H_{c2} is the largest value of solutions which satisfy the condition for a non-trivial solution to exist in these equations of $A_N^{(d,s)}$. As we have mentioned, $|2N\rangle_{d(s)} (N = 0, 1, 2, \dots)$ are involved in the determination of H_{c2} ; however, it is expectable that the first few states such as $|0\rangle_{d(s)}, |2\rangle_{d(s)}$ and $|4\rangle_{d(s)}$ are important because in the case of $c = 0$, $|0\rangle_d, |2\rangle_s$ and $|4\rangle_d$ play the dominant role in determining H_{c2} . Inclusion of more states such as $|6\rangle_{d(s)}$ and $|8\rangle_{d(s)}$ gives rise to a difference much less than 1%.

As we did in Ref.⁶, we introduce dimensionless unit in the calculation of H_{c2} : $t = T/T_c$ and $h = 2|e|H(v_F/2\pi T_c)^2$. In addition to the anisotropy parameter c , we also define parameters $\delta = T_s/T_d$ and $\gamma_z = (2\pi\mu_0^*/ev_F^2)T_c$, which is the strength of spin-magnetic field coupling. For the sake of comparison with experiment measurement, we convert the normalized magnetic field into the dimensional one by using

$$\frac{H(T)}{-\frac{dH}{dT}|_{T_c}T_c} = \frac{h(t)}{-\frac{dh}{dt}|_1}. \quad (24)$$

By solving the eigen-equations for $A_N^{(d,s)}$, we plot H_{c2} in Fig. 1 as a function of temperature for several typical cases. H_{c2} for an anisotropic mixed d - and s -wave superconductor with ZI taken into account is plotted with the solid line. H_{c2} for an anisotropic mixed d - and s -wave superconductor without ZI is represented by the dot-dashed line. The involved parameter values are taken to be: $\delta = T_s/T_d = 0.06$, $c = 0.16$, and $\gamma_z = 0.15$. Also plotted are H_{c2} for a two-dimensional s -wave superconductor (dotted line) and a pure d -wave superconductor (dashed line) without the MA and the ZI. Note that, even though the increase of δ can enhance H_{c2} ,⁶ for the value of δ chosen here, the upper critical field for an isotropic mixed d - and s -wave order parameter (with $\delta = 0.06$) without ZI is more or less same as that of the pure d -wave superconductor (dashed line). As shown in Fig. 1, we find that the mass anisotropy enhances H_{c2} while the spin Zeeman coupling suppresses H_{c2} . This means that the mass anisotropy supports superconductivity; in other words, it increases T_c (and consequently the gap), which can be easily seen from the equation for T_c . In addition, one can also see that H_{c2} is saturated at zero temperature as a reflection of the thermodynamic requirement; namely, on the phase boundary in the $T - H$ plane,

$$-\frac{dH_{c2}}{dT} = \frac{\delta S}{\delta M} = 0 \quad (25)$$

at $T = 0$ near H_{c2} , where δS is the entropy difference between the normal and superconducting states, and δM is the magnetization near H_{c2} .

Recently, the upper critical field H_{c2} (parallel to the c axis) of YBCO with $T_c = 84.3$ K has been measured down to about 4K.⁷ The corresponding data is shown by solid circles in Fig. 1. The slope $dH/dT|_{T_c}$ has been experimentally observed to be -1.9 T/K.⁹ In the theoretical calculation, we are mainly concerned about the low-temperature data of H_{c2} most because at the low temperature thermal fluctuation effect is negligible. As shown in Fig. 1, the experimental data can be fit very well, with the above given parameter values, by our calculation for an anisotropic mixed d - and s -wave superconductor including the ZI. Here we would like to point out that, since δ enhances H_{c2} more significantly than c ,⁶ if we take a large value of δ , we have to choose a physically unacceptable high value of γ_z to fit the low-temperature data. Actually, it is believed that $T_c/E_F \sim 0.1$ for a high- T_c superconductor,¹⁰ which yields $\gamma_z = \pi T_c/2E_F \approx 0.157$ by assuming $\mu_0^* = \mu_B$ (Bohr magneton). On the other hand, most of available experiments seem to indicate that δ should be very small. All this facts demonstrate that the chosen set of parameter values are physically reasonable. Finally, we would like to mention: (i) Because H_p for the sample is about 185 T, the experimental data in Ref.⁷ are within paramagnetic limit¹¹ with the critical ratio H_p/T_c estimated to be 2.2 T/K for a d -wave superconductor. Therefore, in our consideration, we do not have to include the spin-orbit interaction because it reduces the pair-breaking effect of the Zeeman interaction, and consequently, it allows H_{c2} to be larger than H_p .¹² In the theoretical point of view, since the strength of the spin-orbit coupling is proportional to Z^2 , where Z is an atomic number, we may neglect its effect in YBCO as long as no heavy-atomic impurity is taken into account as in this paper. However, it may play an important role in such heavy-fermion superconductors as UBe₁₃ and UPt₃.¹³ (ii) Magnetic and non-magnetic impurities are pair breakers so that it is clear the impurities reduce H_{c2} as well as T_c .¹⁴ However, the impurity concentration in the sample prepared in Ref.⁷ seems to be negligible, the corresponding effect

is not considered here. (iii) Recently, O'brien *et al.*¹⁵ have interpreted the experiment based on a three dimensional s -wave model.¹⁶ However, it is well-known that superconductivity in YBCO is of two dimensional nature.¹ (vi) A small deviation of theoretical results and experimental data occurs in high temperature region because thermodynamic fluctuations¹² of vortices is strong when temperature is high.

In summary, the upper critical field (H_{c2}) of a mixed d - and s -wave superconductor with a mass anisotropy has been microscopically calculated based on the quasiclassical theory. We found the mass anisotropy supports H_{c2} against Zeeman suppression. H_{c2} becomes saturated at zero temperature in consistence with a thermodynamic requirement. The theoretical results are compared well with recent experimental data of $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$.

One of us (W.K.) would like to thank V. Kogan and S. C. Lee for helpful discussions. This work is supported by Texas Center for Superconductivity at the University of Houston and by the Robert A. Welch Foundation.

APPENDIX A:

Since $\Delta_0(\mathbf{R}, \phi) = \Delta_s(\mathbf{R}) + \Delta_d(\mathbf{R}, \phi)$, we have two equations; namely, one is for $\Delta_s(\mathbf{R})$ and the other for $\Delta_d(\mathbf{R})$ as follows:

$$\begin{aligned} \Delta_s(\mathbf{R}) = & V_s \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{1}{[1 + c \sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H \xi) \Omega(\Pi_+, \Pi_-) \Delta_s(\mathbf{R}) \\ & + V_s \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{\sin(2\phi)}{[1 + c \sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H \xi) \Omega(\Pi_+, \Pi_-) \Delta_d(\mathbf{R}) \end{aligned} \quad (\text{A1})$$

and

$$\begin{aligned} \Delta_d(\mathbf{R}) = & V_d \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{\sin(2\phi)}{[1 + c \sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H \xi) \Omega(\Pi_+, \Pi_-) \Delta_s(\mathbf{R}) \\ & + V_d \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{\sin(2\phi)^2}{[1 + c \sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H \xi) \Omega(\Pi_+, \Pi_-) \Delta_d(\mathbf{R}), \end{aligned} \quad (\text{A2})$$

where

$$\Omega(\Pi_+, \Pi_-) = 2\pi T N_0 \exp[-i \text{sgn}(\omega) \left(\frac{v_F}{\sqrt{2}} \right) \xi] \{ (e^{-i\phi} - i c e^{i\phi}) \Pi_+ + (e^{i\phi} + i c e^{-i\phi}) \Pi_- \} \quad (\text{A3})$$

with $\Pi_{\pm} = (\Pi_x \pm i\Pi_y)/\sqrt{2}$. Note that

$$\begin{aligned} & [-i\text{sgn}(\omega) \left(\frac{v_F}{\sqrt{2}} \right) \xi(e^{-i\phi} - ice^{i\phi})\Pi_+, -i\text{sgn}(\omega) \left(\frac{v_F}{\sqrt{2}} \right) \xi(e^{i\phi} + ice^{-i\phi})\Pi_-] \\ &= 2|e|H \left(\frac{v_F\xi}{\sqrt{2}} \right)^2 [1 + 2c\sin(2\phi) + c^2], \end{aligned} \quad (\text{A4})$$

then we obtain

$$\begin{aligned} \Delta_s(\mathbf{R}) &= V_s \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{1}{[1 + c\sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H\xi) \tilde{\Omega}(\Pi_+, \Pi_-) \Delta_s(\mathbf{R}) \\ &+ V_s \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{\sin(2\phi)}{[1 + c\sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H\xi) \tilde{\Omega}(\Pi_+, \Pi_-) \Delta_d(\mathbf{R}) \end{aligned} \quad (\text{A5})$$

and

$$\begin{aligned} \Delta_d(\mathbf{R}) &= V_d \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{\sin(2\phi)}{[1 + c\sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H\xi) \tilde{\Omega}(\Pi_+, \Pi_-) \Delta_s(\mathbf{R}) \\ &+ V_d \sum_{\omega} \int \frac{d\phi}{2\pi} \frac{\sin(2\phi)^2}{[1 + c\sin(2\phi)]} \int d\xi e^{-2|\omega|\xi} \cos(2\mu_0^* H\xi) \tilde{\Omega}(\Pi_+, \Pi_-) \Delta_d(\mathbf{R}), \end{aligned} \quad (\text{A6})$$

where

$$\begin{aligned} \tilde{\Omega}(\Pi_+, \Pi_-) &= 2\pi T N_0 \exp \left[-|e|H \left(\frac{v_F\xi}{\sqrt{2}} \right)^2 (1 + 2c\sin(2\phi) + c^2) \right] \\ &\times e^{-i\text{sgn}(\omega) \left(\frac{v_F}{\sqrt{2}} \right) \xi(e^{-i\phi} - ice^{i\phi})\Pi_+} e^{-i\text{sgn}(\omega) \left(\frac{v_F}{\sqrt{2}} \right) \xi(e^{i\phi} + ice^{-i\phi})\Pi_-}. \end{aligned} \quad (\text{A7})$$

Expanding $\Delta_{s(d)}(\mathbf{R})$ in terms of $\{f_N(\mathbf{R})\}$ and noting

$$\begin{pmatrix} \Pi_+ \\ \Pi_- \end{pmatrix} f_N = \sqrt{2|e|H} \begin{pmatrix} \sqrt{N+1} \\ \sqrt{N} \end{pmatrix} \begin{pmatrix} f_{N+1} \\ f_{N-1} \end{pmatrix}, \quad (\text{A8})$$

we obtain Eqs. (17) and (18).

REFERENCES

- ¹ For a review, see D. J. Scalapino, Phys. Rep. **250**, 329 (1995) for theory, and D. J. Van Harlingen, Rev. Mod. Phys. **67**, 515 (1995) for experiment.
- ² W. A. Atkinson and J. P. Carbotte, Phys. Rev. B **52**, 10601 (1995).
- ³ J.-H. Xu, Y. Ren and C. S. Ting, Int. J. Mod. Phys. **10**, 2699 (1996).
- ⁴ W. Belzig, C. Bruder and M. Sigrist, Phys. Rev. Lett. **80**, 4285 (1998).
- ⁵ G. Eilenberger, Z. Phys. **241**, 195 (1968).
- ⁶ W. Kim, J.-X. Zhu and C. S. Ting, Phys. Rev. B **58**, R607 (1998).
- ⁷ H. Nakagawa, T. Takamasu, N. Miura and Y. Enomoto, Physica B **246-247**, 429 (1998).
- ⁸ C. T. Rieck, K. Scharnberg and N. Schopohl, J. Low Temp. Phys. **84**, 381 (1991).
- ⁹ U. Welp, W. K. Kwok, G. W. Crabtree, K. G. Vandervoort and J. Z. Liu, Phys. Rev. Lett. **62**, 1908 (1989).
- ¹⁰ V. Z. Kresin and S. A. Wolf, in *Novel superconductor*, edited by S. A. Wolf and V. Z. Kresin (Plenum press, 1987).
- ¹¹ A. M. Clongston, Phys. Rev. Lett. **9**, 266 (1962); B. S. Chandrasekhar, Appl. Phys. Lett. **1**, 7 (1962).
- ¹² M. Tinkham, *Introduction to superconductivity* (McGraw-Hill, New York, 1996).
- ¹³ M. Sigrist and K. Ueda, Rev. Mod. Phys. **63**, 239 (1991).
- ¹⁴ G. Yin and K. Maki, Physica B **194-196**, 2025 (1994).
- ¹⁵ J. L. O'brien, H. Nakagawa, A. S. Dzurak, R. G. Clark, B. E. Kane, N. E. Lumpkin, N. Miura, E. E. Mitchell, J. D. Goettee, J. S. Brooks, D. G. Rickel and R. P. Starrett, cond-mat/9901341.

¹⁶ E. Helfand and N. R. Werthamer, Phys. Rev. **147**, 288 (1966); N. R. Werthamer, E. Helfand and P. C. Hohenberg, Phys. Rev. **147**, 295 (1966).

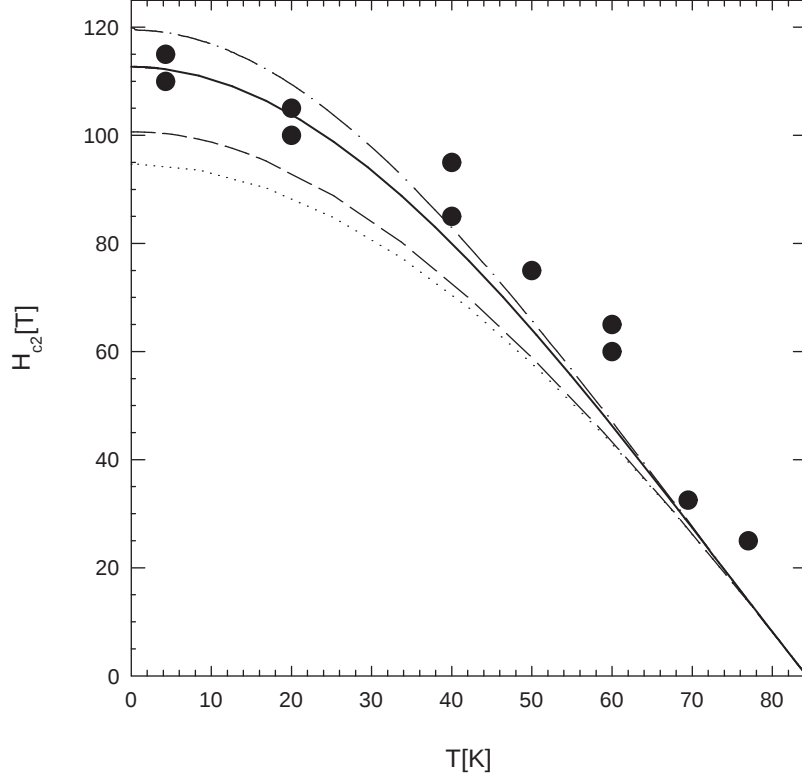


FIG. 1. The upper critical field H_{c2} for an anisotropic mixed d - and s -wave superconductor (solid line) with the spin Zeeman interaction taken into account. Solid circles are experimental data of YBCO⁷. Also plotted are H_{c2} of a two-dimensional isotropic s -wave superconductor (dotted line), a pure isotropic d -wave superconductor (dashed line), and an anisotropic mixed d - and s -wave superconductor (dot-dashed line), all obtained without the Zeeman interaction included.